

## MÖSSBAUER SPECTRA OF DIOCTAHEDRAL SMECTITES

I. ROZENSON and L. HELLER-KALLAI

Department of Geology, Hebrew University, Jerusalem, Israel

(Received 8 September 1976; and in revised form 22 November 1976)

**Abstract**—Mössbauer spectra of 15 smectites were investigated. In these samples, ferric iron occupies both M(1) and M(2) octahedral sites, the distribution being partly determined by the relative covalency of the bonds formed.

The quadrupole splittings are linearly related to  $b^{-3}$ . They show that  $Fe^{3+}$  octahedra are much more distorted in montmorillonite and beidellite than in nontronite and volkonskoite and that M(1) sites are more prone to change than M(2). Ferrous iron occurs in relatively undistorted octahedra in some otherwise distorted octahedral sheets and vice versa.

### INTRODUCTION

In recent years, Mössbauer spectroscopy has become a tool of increasing importance in mineralogy. The spectra of clay minerals have been described in various publications (Weaver *et al.*, 1967; Taylor *et al.*, 1968; Cousins and Dharmawardena, 1969; Malathi and Puri, 1969; Kohyama *et al.*, 1972; Brunot, 1973; Coey, 1975; Tennakoon *et al.*, 1974; Goodman *et al.*, 1976). Many of the descriptions are qualitative, centering on the determination of the  $Fe^{2+}/Fe^{3+}$  ratio. Goodman *et al.* used Mössbauer spectroscopy to ascertain the amount of tetrahedrally coordinated iron. In the present study, an attempt is made to establish relationships between some parameters of the Mössbauer spectra of dioctahedral smectites and their structures.

### METHODS OF INVESTIGATION

X-ray diffractometer traces of unoriented samples containing quartz as internal standard were used to determine  $d_{060}$  and of oriented specimens for mineralogical identification.

Mössbauer spectra were obtained using a  $^{57}Co$  in Pd source with a 255 channel analyser. Between  $2 \times 10^6$  to  $4 \times 10^6$  counts per channel were accumu-

lated for each spectrum. Samples containing about 5 mg of iron per  $cm^2$  were ground with glucose to prevent preferred orientation. Both sample and source were at room temperature. Center shifts are quoted relative to Pd.

The spectra were fitted to two or three doublets, corresponding to  $Fe^{3+}$  in two sites or  $Fe^{3+}$  in two sites and  $Fe^{2+}$  in one site, respectively. Resolution of the  $Fe^{2+}$  or addition of a further  $Fe^{3+}$  doublet did not reduce the values of  $\chi^2$ . In the final fit the only constraints imposed were equal  $Fe^{3+}$  line widths, but these were allowed to differ from the  $Fe^{2+}$  line width.

### MINERALOGICAL COMPOSITION

The samples studied are composed predominantly of smectites associated with minor amounts of impurities (Table 1). A sample of metabentonite was also investigated.

Experiments showed that even mild chemical treatment, such as cation exchange, affects the oxidation state of iron in smectites (paper in preparation). No attempt was made, therefore, to separate size fractions in aqueous suspension or to purify the samples. From the point of view of Mössbauer spectroscopy the impurities may be divided into two categories: those which contain appreciable amounts of iron and those

Table 1. Mineralogical composition of samples from various localities

No	Smectite	Locality	Impurities
1	M	Wyoming, U.S.A. (S.C.M.)	Quartz, K-Felspar
2	M	Wyoming, U.S.A. (S.C.M.)	Quartz, K-Felspar
3	M	Ramon, Israel (Frenkel, 1975)	Illite, quartz, iron oxides
4	M	Mississippi, U.S.A. (Ward's)	Quartz
5	M	Camp Bertaux, Morocco	—
6	M	Texas, U.S.A.	Quartz, iron oxides
7	M	Texas, U.S.A. (S.C.M.)	—
8	M	Cameron, Arizona, U.S.A. (Ward's)	Quartz, kaolinite
9	M	Belle Fourche, U.S.A. (Ward's)	—
10	M	Almaria, Spain	Quartz, plagioclase
11	B.S.	Scan Raft, Sweden	—
12	B.S.	Scan Raft, Sweden	—
13	N	Washington, U.S.A. (S.C.M.)	Quartz, iron oxides
14	V	Bahia, Brazil (Besnus <i>et al.</i> , 1975)	Chlorite
15	M.B.	High Bridge, Kentucky, U.S.A. (Ward's)	Quartz

Abbreviations: M = montmorillonite, B.S. = beidellitic smectite, N = nontronite, V = volkonskoite, M.B. = metabentonite, S.C.M. = Source Clay Minerals Project.

Table 2. Mössbauer parameters of the samples studied

No.	Smectite	Fe <sup>3+</sup> in M(1) ( <i>trans</i> configuration)				Fe <sup>3+</sup> in M(2) ( <i>cis</i> configuration)				Fe <sup>2+</sup>		(12) $\chi^2$	
		(1) I.S.	(2) Q.S.	(3) $\Gamma$	(4) I.S.	(5) Q.S.	(6) $\Gamma$	(7) I.S.	(8) Q.S.	(9) $\Gamma$	(10) Fe <sup>2+</sup> / Fe <sup>3+</sup>		(11) AM(1)/ AM(2)
1	M	0.12 ± 0.02	1.32 ± 0.03	0.48 ± 0.03	0.09 ± 0.00	0.57 ± 0.02	0.48 ± 0.03	0.89 ± 0.01	3.00 ± 0.03	0.46 ± 0.02	0.45	0.30	310
2	M	0.12 ± 0.01	1.29 ± 0.03	0.49 ± 0.02	0.09 ± 0.01	0.61 ± 0.03	0.49 ± 0.02	0.88 ± 0.01	2.95 ± 0.03	0.46 ± 0.02	0.39	0.26	290
3	M	0.20 ± 0.09	1.22 ± 0.02	0.41 ± 0.03	0.18 ± 0.01	0.45 ± 0.02	0.41 ± 0.03	—	—	—	—	0.80	360
4	M	0.16 ± 0.01	1.07 ± 0.02	0.44 ± 0.02	0.11 ± 0.01	0.57 ± 0.02	0.44 ± 0.02	—	—	—	—	0.18	280
5	M	0.14 ± 0.01	0.99 ± 0.02	0.49 ± 0.04	0.10 ± 0.01	0.53 ± 0.03	0.49 ± 0.04	—	—	—	—	0.36	273
6	M	0.23 ± 0.01	1.16 ± 0.02	0.48 ± 0.03	0.11 ± 0.00	0.54 ± 0.02	0.48 ± 0.03	—	—	—	—	0.16	280
7	M	0.12 ± 0.01	1.03 ± 0.03	0.44 ± 0.03	0.18 ± 0.01	0.53 ± 0.03	0.44 ± 0.03	—	—	—	—	0.80	290
8	M	0.13 ± 0.01	0.85 ± 0.02	0.51 ± 0.03	0.11 ± 0.02	0.49 ± 0.03	0.51 ± 0.03	—	—	—	—	0.38	260
9	M	0.24 ± 0.02	1.09 ± 0.02	0.50 ± 0.03	0.12 ± 0.01	0.56 ± 0.02	0.50 ± 0.03	0.89 ± 0.01	2.80 ± 0.03	0.39 ± 0.02	0.44	0.43	265
10	M	0.15 ± 0.01	1.26 ± 0.02	0.47 ± 0.03	0.11 ± 0.01	0.43 ± 0.03	0.47 ± 0.03	0.90 ± 0.01	2.76 ± 0.02	0.33 ± 0.02	0.07	0.20	270
11	B.S.	0.30 ± 0.01	1.35 ± 0.02	0.56 ± 0.04	0.12 ± 0.01	0.59 ± 0.03	0.56 ± 0.04	0.92 ± 0.01	2.74 ± 0.03	0.34 ± 0.02	0.21	0.07	268
12	B.S.	0.19 ± 0.01	1.28 ± 0.02	0.56 ± 0.03	0.10 ± 0.01	0.56 ± 0.02	0.56 ± 0.03	0.89 ± 0.01	2.56 ± 0.03	0.46 ± 0.01	0.14	0.19	280
13	N	0.09 ± 0.00	0.70 ± 0.02	0.39 ± 0.01	0.08 ± 0.00	0.28 ± 0.02	0.39 ± 0.01	—	—	—	—	0.50	260
14	V	0.14 ± 0.00	0.72 ± 0.02	0.35 ± 0.03	0.15 ± 0.01	0.31 ± 0.03	0.35 ± 0.03	—	—	—	—	0.90	273
15	M.B.	—	—	—	0.14 ± 0.00	0.62 ± 0.02	0.45 ± 0.01	—	—	—	—	—	270

Abbreviations: M, B.S., V and M.B. as in Table 1. I.S. = isomer shift relative to Pd; Q.S. = quadrupole splitting;  $\Gamma$  = peak width, all in mm/sec, AM(1)/AM(2) = ratio of amount of Fe<sup>3+</sup> in sites M(1) to that in sites M(2).

which do not. Quartz, calcite and feldspar, though relatively abundant, do not affect the Mössbauer spectra, whereas iron oxides coating the clay particles or admixed micaceous impurities may do so.

Iron oxides are difficult to detect by X-ray methods, due to their fine particle size. In Mössbauer spectra they may give rise to a magnetic six-line pattern at low temperatures, but may show a paramagnetic pattern at room temperature. If the particles are sufficiently large, the six-line pattern will also appear at room temperature. Of the samples examined only No. 8 shows a magnetic spectrum at room temperature. This practically disappears on treatment of the sample with dilute HCl. Chemical analysis using the method of Mitchell and Mackenzie (1954) demonstrated that the amount of iron in the coating did not exceed 5% of the total. In the other samples examined, it ranged from 0 to 3%.

Micaceous impurities, if present, are below the limits of detection of X-ray and i.r. methods. Only iron-rich micas, therefore, could affect the Mössbauer spectra significantly. Since most of the iron in smectites is trivalent, the greater error would be expected in the  $\text{Fe}^{2+}$  parameters. It is shown below (Table 2) that only five of the samples contain appreciable amounts of  $\text{Fe}^{2+}$ . Of these, montmorillonite from Wyoming (samples 1 and 2) and the beidellitic smectites (samples 11 and 12) have been investigated in detail in previous studies (Rozenon and Heller-Kallai, 1976; Bystrom-Brusewitz, 1975) without any indication of the presence of iron-containing impurities. Only in sample No. 9 can the presence of  $\text{Fe}^{2+}$  containing impurities not be entirely excluded, though no evidence for their presence was found either in this or in a previous study (API Project 49).

#### THE MÖSSBAUER SPECTRA

A typical spectrum is shown in Figure 1 and the calculated parameters are given in Table 2. Most of the spectra recorded show only one broad doublet,

with parameters characteristic of  $\text{Fe}^{3+}$ . Some samples give rise to an additional, smaller doublet corresponding to  $\text{Fe}^{2+}$ . The strong doublet generally could be resolved into two, with isomer shifts and quadrupole splittings typical of octahedrally coordinated  $\text{Fe}^{3+}$  (Bancroft, 1974). There is no evidence for the presence of tetrahedrally coordinated iron in any of the samples we investigated. Goodman *et al.* (1976) found tetrahedral iron in all the nontronites they examined, including a specimen of sample 13, for which they report 6% tetrahedrally coordinated  $\text{Fe}^{3+}$ . Our data for a two-doublet fit resemble those of Goodman *et al.*, but no improvement in  $\chi^2$  was achieved by addition of a further doublet. We therefore concluded that no tetrahedral iron was present, in agreement with the results of our wet chemical analysis and the microprobe analysis of Goodman *et al.* The original sample is inhomogeneous and our specimen may differ slightly from that studied by Goodman *et al.* Moreover, as pointed out by these authors, there is considerable uncertainty in the interpretation of all the data, and the presence of less than about 5% tetrahedrally coordinated iron in any of the samples we studied cannot be ruled out.

Each unit cell of smectites contains three possible octahedral sites: M(1), with hydroxyl groups arranged in *trans* positions and two sites M(2) with hydroxyl groups arranged in *cis* positions. In the ideal structure, the two M(2) sites are equivalent. In fact, the symmetry of these sites may differ, as, for example, in 3T muscovite (Güven and Burnham, 1967). The question therefore arises whether the two  $\text{Fe}^{3+}$  doublets should be assigned to M(1) and M(2) sites or to two non-equivalent M(2) sites. Simple calculations show that for a square bipyramidal arrangement of groups like  $\text{Fe}^{3+}\text{A}_2\text{B}_4$  the absolute value of the ratio of the quadrupole splitting for the *trans* to that of the *cis* configuration is 2. The ratio observed for the two  $\text{Fe}^{3+}$  doublets in the smectite spectra is close to 2 (see below). This suggests that the first alternative is the more probable. It was also adopted for non-

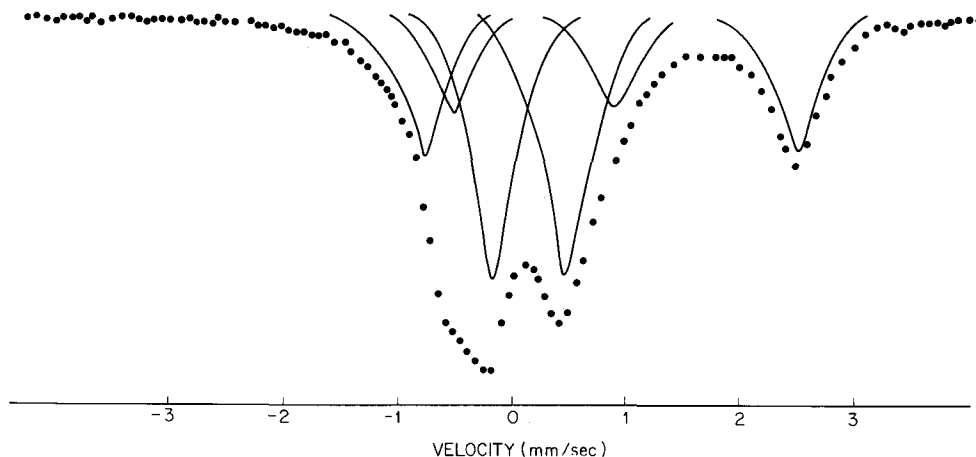


Figure 1. Mössbauer spectrum of montmorillonite (sample No. 1) fitted to three octahedral doublets—two  $\text{Fe}^{3+}$  and one  $\text{Fe}^{2+}$ .

tronites by Goodman *et al.* (1976). The possibility remains, however, that there are three independent octahedral sites, although attempts to resolve the spectra accordingly did not give meaningful results.

The line widths of both  $\text{Fe}^{3+}$  doublets (Table 2) are generally greater than 0.38 mm/sec, the width reported for  $\text{Fe}^{3+}$  in most other silicates (Bancroft, 1974). It seems that each doublet corresponds to several sites of slightly different symmetry with similar but not identical Mössbauer parameters (Rozenon and Heller-Kallai, 1976). These sites may occur within the same octahedral sheet or in different layers of the same mineral.

The  $\text{Fe}^{2+}$  doublets are symmetrical. The doublet for samples 10 and 11 is relatively narrow. In contrast, it is broad for samples 1, 2 and 12, but  $\chi^2$  could not be decreased by resolution into two doublets. This suggests that  $\text{Fe}^{2+}$  in samples 1, 2 and 12 occupies several similar sites, M(1) or M(2), but that the range of electric field gradients is more limited in sample 9 and even more so in samples 10 and 11.

A small error in the Mössbauer parameters may be introduced by the presence of minor amounts of iron oxides in some of the samples, as discussed, but since the amount of iron in this phase never exceeded 5% of the total, this error is probably negligible.

#### QUADRUPOLE SPLITTING (Q.S.)

The quadrupole splitting in a Mössbauer spectrum of  $^{57}\text{Fe}$  is given by the equation

$$\text{Q.S.} = \frac{1}{2}e^2qQ\left(1 + \frac{\eta^2}{3}\right)^{1/2},$$

where Q.S. is the quadrupole splitting,  $Q$  is the quadrupole moment of the nucleus,  $e^2q$  (or  $V_{zz}$ ) is the  $z$  component of the electric field gradient (EFG) tensor and  $\eta = [(V_{xx} - V_{yy})/V_{zz}]$  is the asymmetry parameter.

$V_{xx}$ ,  $V_{yy}$  and  $V_{zz}$  are the components of the EFG tensor in three mutually perpendicular directions.

Two factors determine the magnitude of  $q$ : the contribution of the surrounding ligand ( $q_{\text{lattice}}$ ) and the distribution of the valence electrons ( $q_{\text{valence}}$ ), i.e.

$$q = (1 - \gamma\infty)q_{\text{lattice}} + (1 - R)q_{\text{valence}}$$

where  $\gamma\infty$  and  $R$  are empirical constants.

$\text{Fe}^{3+}$  in silicates occurs in the high spin, spherically symmetrical electronic configuration  $(t_{2g})^3(e_g)^2$ .  $q_{\text{valence}}$  is therefore equal to zero.  $q_{\text{lattice}}$  is proportional to  $r^{-3}$ , where  $r$  is the ligand-cation distance, and to a trigonometric function which depends upon the ligand-cation configuration. For a square bi-pyramidal arrangement,  $\text{MA}_2\text{B}_4$ , the absolute ratio  $K$  between the quadrupole splittings of atoms in *trans* to those in *cis* sites is 2:1. The derivation is based on three assumptions: (1)  $\eta$ , the asymmetry factor, is zero; (2) the charges involved are point charges or the bonding is of the  $\sigma$  type; (3) the contribution to the quadrupole splitting from parts of the structure other than nearest neighbours can be neglected (Bancroft, 1974).

Figure 2 is a plot of the quadrupole splitting of  $\text{Fe}^{3+}$  in one of the trivalent sites of the smectile relative to that in the other. It is evident that, for the smectites studied, the value of  $K$  is either equal to or close to two. This indicates that for some of the samples, at least, the above assumptions are valid. In samples for which  $K$  differs from 2, the octahedra are probably distorted. This may involve some  $\pi$  bonding analogous to that postulated for pyroxenes (O'Nions and Smith, 1973) and a more significant effect of the next nearest neighbours. It is difficult to judge which of these factors are the cause and which the effect of the configuration adopted by the mineral.

The magnitude of the Q.S. of the M(1) doublets is large for the montmorillonites and beidellitic smectites, indicating that the octahedra are very distorted. Moreover, the range of magnitudes of the Q.S. of

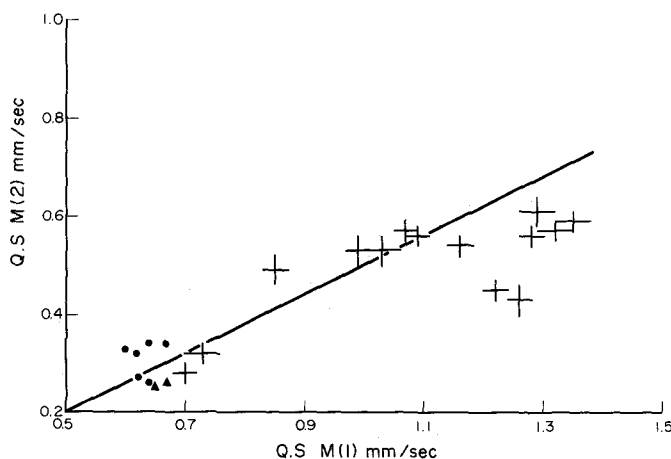


Figure 2. Relationship between quadrupole splitting of  $\text{Fe}^{3+}$  in M(1) and M(2) sites. + data obtained in this study (the magnitude of the line represents the error),  $\blacktriangle$ —Brunot (1973),  $\bullet$ —Goodman *et al.* (1976).

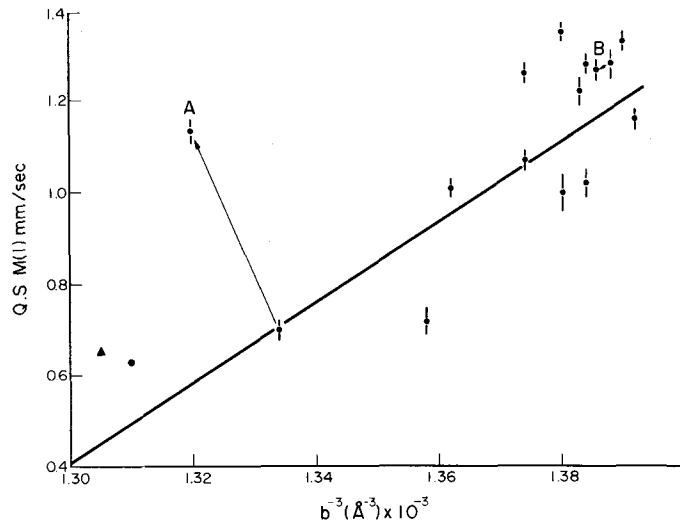


Figure 3. Dependence of quadrupole splitting of  $\text{Fe}^{3+}$  in M(1) sites on  $b^{-3}$ . Legend as for Figure 2. For explanation of points A and B see text.

$\text{Fe}^{3+}$  in the M(2) and, in particular, in the M(1) series (Table 2) is greater than in other mineral groups, e.g. amphiboles (Ernst and Wai, 1970). In the nontronite series studied by Goodman *et al.* (1976) these differences are relatively small. It appears that in montmorillonites and beidellites, both M(1) and M(2) sites are sensitive to structural changes of the minerals. The larger differences in Q.S. suggest that the M(1) sites are the more easily deformed. This is plausible in view of the fact that in dioctahedral phyllosilicates M(1) sites are generally larger than M(2), rendering them more prone to distortion. It appears that octahedral layers occupied by the larger cations  $\text{Fe}^{3+}$  and/or  $\text{Cr}^{3+}$  (sample 14) are less distorted.

Figures 3 and 4 show the relationship between the  $b$  repeat distance and the Q.S. of  $\text{Fe}^{3+}$  in sites M(1) and M(2), respectively. The plots of Q.S. against  $b^{-3}$  are approximately linear, with correlation coefficients of 0.910 and 0.898, respectively. Simple calculations show that the values of Q.S. are more sensitive to

changes in bond angles than bond lengths. To account for a difference of about 50% in Q.S., as observed between some montmorillonites and beidellites on the one hand and nontronites on the other, an increase in  $\text{Fe}^{3+}-\text{O}$  bond length of at least 27% would be required. Since this is not reasonable, it must be inferred that differences in Q.S. are largely due to distortions of the octahedra, which govern the values of  $\eta$ , in agreement with the postulates of Radoslovich and Norrish (1962), that changes in bond angles occur in preference to changes in bond lengths. Since  $b$  is determined by the chemical composition, so also is the Q.S. The Mössbauer spectra clearly demonstrate that the octahedral sheets of montmorillonite and beidellite are very distorted, but those of nontronite and volkonskoite much less. This conclusion is not unexpected, but Mössbauer spectra provide the possibility of interpreting the phenomena quantitatively. This will be attempted in a separate study.

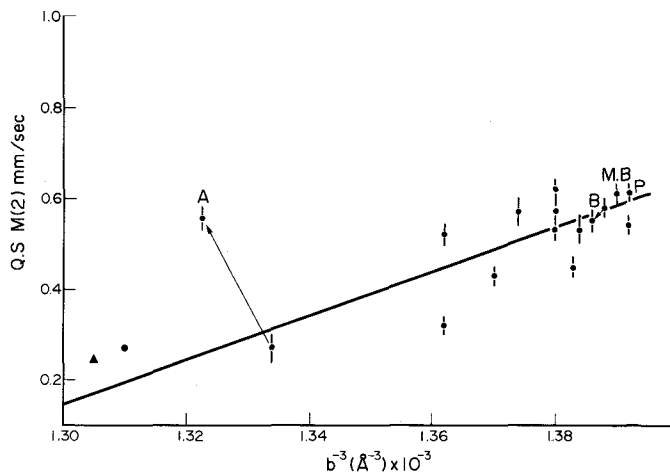


Figure 4. Dependence of quadrupole splitting of  $\text{Fe}^{3+}$  in M(2) sites on  $b^{-3}$ . Legend as for Figure 2. For explanation of points A, B, MB and P see text.

Exchange of interlayer cations has a small but significant effect on the Mössbauer parameters. The points corresponding to sample 1 saturated with various cations fall on the straight lines, but, for clarity, are not included in the figures. Points corresponding to metabentonite (MB, sample 15) and to pyrophyllite (P), for which the parameters were taken from the literature (Wardle and Brindley, 1970; Hogg and Meads, 1970) and which contain  $\text{Fe}^{3+}$  in M(2) sites only, fall on the straight line of Figure 4, as shown.

Two further points, A and B, are plotted on the graphs, corresponding, respectively, to nontronite (sample 13) and montmorillonite (sample 1) reduced with  $\text{Na}_2\text{S}_2\text{O}_4$  and reoxidized. Point A does not fall on the straight lines, whereas point B does. An additional point C, corresponding to montmorillonite heated at  $700^\circ\text{C}$  lies completely outside the range of the diagrams, with Q.S. = 1.40 mm/sec,  $b^{-3} = 1.13 \cdot 10^{-3} \text{Å}^{-3}$ . It was previously shown that reduction with  $\text{Na}_2\text{S}_2\text{O}_4$  decreases the coordination number of some of the ions in the octahedral sheet of nontronite to five irreversibly, but in montmorillonite no such change occurs (Rozenon and Heller-Kallai, 1976). Heating at  $700^\circ\text{C}$  causes dehydroxylation of smectites, which involves a change to five-coordination of all the octahedral cations. Points corresponding to reduced or reduced and reoxidized montmorillonites, like point B, therefore fall near the straight lines of Figures 3 and 4, while the drastic structural changes involved in reduction of nontronite and, even more, on dehydroxylation of the smectites, account for the deviation of points A and C from the straight lines.

$\text{Fe}^{2+}$  is not a spherically symmetrical ion and the  $q_{\text{valence}}$  term cannot be neglected. It is therefore more difficult to interpret the quadrupole splittings obtained for  $\text{Fe}^{2+}$  quantitatively. In general, the smaller the value of the Q.S., the greater the distortion of the  $\text{Fe}^{2+}$  octahedra.

The Q.S. for  $\text{Fe}^{2+}$  in the smectites examined ranges from 3.00 mm/sec in sample 1 to 2.56 mm/sec in sample 12, indicating that the  $\text{Fe}^{2+}$  octahedra are more distorted in sample 12 than in sample 1. There is no apparent correlation between the symmetry of the sites occupied by  $\text{Fe}^{3+}$  and  $\text{Fe}^{2+}$  ions. The high values of the Q.S. of  $\text{Fe}^{3+}$  in samples 1, 2, 10, 11 and 12 indicate that these sites are very distorted. The sites occupied by  $\text{Fe}^{2+}$  in samples 10, 11 and 12 are also distorted, but those in samples 1 and 2 are considerably more regular. Moreover, when additional  $\text{Fe}^{2+}$  ions were produced by reduction of samples 1 and 2 with hydrazine, this also occupied relatively undistorted sites (Rozenon and Heller-Kallai, 1976). In contrast, on reduction of nontronite (sample 13) with hydrazine,  $\text{Fe}^{2+}$  is formed which gives rise to a Q.S. of 2.64–2.67 mm/sec, indicating that the octahedra are appreciably distorted. It is noteworthy that  $\text{Fe}^{2+}$  occupies relatively undistorted sites in the otherwise distorted octahedral sheets of samples 1 and 2, but not of 10, 11 and 12, and occu-

pies irregular octahedra in the otherwise relatively symmetrical sheets of nontronite.

#### ISOMER SHIFT (I.S.)

The isomer shifts for  $\text{Fe}^{3+}$  in the various smectites differ, though they all fall in the region commonly assigned to six-coordinated  $\text{Fe}^{3+}$  in silicates. The values for  $\text{Fe}^{3+}$  in M(2) range from 0.08–0.18 mm/sec, clustering around 0.10–0.12 mm/sec, while those for  $\text{Fe}^{3+}$  in M(1) sites cover a wider range, from 0.09 to 0.25 mm/sec. For montmorillonites and beidellitic smectites the I.S. in position M(1) exceeds that in M(2), whereas for nontronites and volkonskoite all the isomer shifts are similar (Table 1 and Goodman *et al.*, 1976).

The I.S. arises from the interaction between the nucleus and the overlapping electron orbitals. The lower the I.S. for  $\text{Fe}^{3+}$ , the greater the covalent contribution to the  $\text{Fe}^{3+}$ -ligand bond. In montmorillonites and beidellites  $\text{Fe}^{3+}$  occupying M(2) sites is thus more covalently bonded than  $\text{Fe}^{3+}$  in M(1) sites. This is reasonable in view of the fact that the M(2) sites in dioctahedral minerals are usually smaller, thus permitting stronger overlap between metal and ligand orbitals. It appears that when the octahedral sheets are predominantly occupied by the relatively large cations  $\text{Fe}^{3+}$  and  $\text{Cr}^{3+}$ , sites M(1) and M(2) become very similar, as was also indicated by the quadrupole splittings.

The differences between the various smectites may be due to the effect of next nearest neighbours, though no direct correlation could be established between the chemical composition and the observed isomer shifts. The wider range of values for  $\text{Fe}^{3+}$  in M(1), like that of the Q.S., suggests that this site is the more susceptible to structural changes. In the absence of accurate structure determinations of smectites, it is futile to attempt a more quantitative treatment at this stage.

The isomer shifts of all the  $\text{Fe}^{2+}$  doublets are similar.

#### DISTRIBUTION OF $\text{Fe}^{3+}$ BETWEEN M(1) AND M(2) SITES

The ratio of the amount of  $\text{Fe}^{3+}$  occupying M(1) to that occupying M(2) sites ( $A_{\text{M}(1)}/A_{\text{M}(2)}$ ) is shown in column 11 of Table 2. Since there are twice as many M(2) sites as there are M(1), the ratio of 0.5 indicates completely random distribution of  $\text{Fe}^{3+}$  between M(1) and M(2). The values range from zero, corresponding to a structure in which  $\text{Fe}^{3+}$  occupies M(2) exclusively, to 0.9, indicating strong preference for M(1) sites. The errors in these values are relatively large, because the areas of the doublets, which are taken to be proportional to the amount of  $\text{Fe}^{3+}$ , are very sensitive to small changes in the Mössbauer parameters.

Figure 5 shows the relationship between the ratio  $A_{\text{M}(1)}/A_{\text{M}(2)}$  and the difference in I.S. for  $\text{Fe}^{3+}$  in M(1) and M(2) sites for 14 of the 15 samples examined.

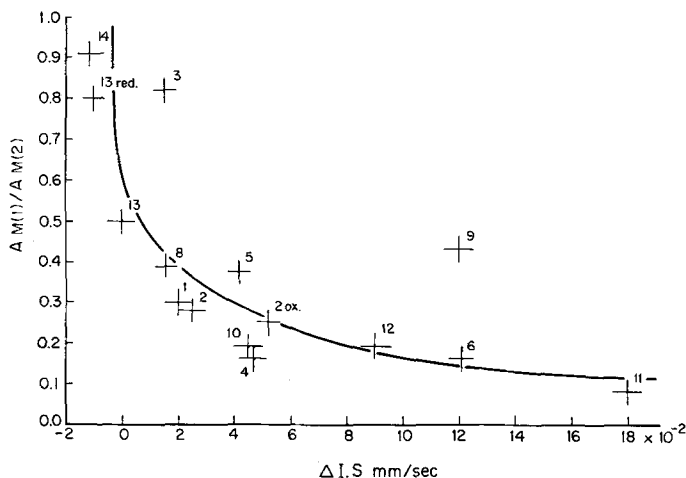


Figure 5. Distribution of  $\text{Fe}^{3+}$  in octahedral sheets. Legend as for Figure 2. The numbers correspond to those in Table 1. ox = oxidized, r = reduced.

In general, the smaller the difference, the greater the tendency for  $\text{Fe}^{3+}$  to occupy M(1) sites, i.e. the more nearly the covalency of  $\text{Fe}^{3+}$  in site M(1) resembles that in M(2), the greater the tendency for this site to be populated. It appears that in the absence of crystal field stabilization, which is precluded by the electronic structure of  $\text{Fe}^{3+}$ , the tendency to form more covalent Fe–O bonds is a decisive factor in determining the distribution of  $\text{Fe}^{3+}$  among the available sites. Sample No. 7 does not conform to the relationship. It contains very little iron and requires further examination.

Data presented in Table 2 of the paper by Goodman *et al.* (1976) show that for nontronites the difference in I.S. between sites M(1) and M(2) is close to zero and  $A_{M(1)}/A_{M(2)}$  ranges from 0.33 to 0.68. It thus appears that with nontronites other factors, e.g. tetrahedral site occupancy, must also be taken into account.

Cation ordering in layer silicates has been extensively studied and was recently reviewed by Bailey (1975) who claimed that all dioctahedral silicates have ordered vacant octahedral sites. Selected area diffraction patterns have shown that the elementary layers of montmorillonite are non-centrosymmetric, while those of nontronite and beidellite are centro-symmetric (Mering and Oberlin, 1971; Güven and Pease, 1975). It was concluded that the octahedral cations in montmorillonite occupy equal numbers of M(1) and M(2) sites, while in nontronite and beidellite only M(2) sites are occupied. It should be stressed that the electron optical investigations relate to all the octahedral cations, whereas the present study is confined only to octahedral  $\text{Fe}^{3+}$ . Our data are thus compatible with the electron optical data for montmorillonite, but not for nontronite, as reported previously (Rozenon and Heller-Kallai, 1976). For the beidellitic smectites, the Mössbauer spectra indicate almost complete preference for M(2) sites, in agreement with the electron-optical data. The presence of minor amounts of  $\text{Fe}^{3+}$  in M(1) positions in our

samples may be due to the fact that they were not true beidellites. Unfortunately, no true beidellites were available. In the various montmorillonites  $\text{Fe}^{3+}$  ions occupy different proportions of M(1) and M(2) sites, but since these constitute only a small fraction of the octahedral cations, the results are compatible with the electron optical data, though they do not necessarily confirm them. In nontronite, however,  $\text{Fe}^{3+}$  is the dominant octahedral cation and its random distribution between the two sites is incompatible with the centro-symmetric configuration inferred from the electron optical data. As previously suggested (Goodman *et al.*, 1976; Rozenon and Heller-Kallai, 1976) it seems probable that nontronite is built of domains, in some of which  $\text{Fe}^{3+}$  occupies M(1) and M(2) sites equally and in others M(1) sites only. These may occur within the same sheet, as suggested by Goodman *et al.*, or in the octahedral sheets of different layers.

In metabentonite, which is composed of illite and a mixed-layer illite-smectite,  $\text{Fe}^{3+}$  occupies M(2) sites exclusively. This does not, however, necessarily apply to all the other octahedral cations. Metabentonite shows the same relationship between Q.S. and  $b^{-3}$  as the smectites and may thus be regarded as the end-member of the series of smectites studied.

## CONCLUSIONS

The absolute ratio of the quadrupole splittings of  $\text{Fe}^{3+}$  in *cis* and *trans* sites of dioctahedral smectites is approximately 1:2, as predicted by theory. The actual values, which vary widely throughout the series, show that the octahedra are very distorted in montmorillonites and beidellites and considerably less in nontronites and volkonskoite, in agreement with the concepts of Radoslovich and Norrish (1962). The larger  $\text{Fe}^{2+}$  ions, however, occupy relatively symmetrical sites in some montmorillonites and more distorted sites in hydrazine reduced nontronites, in which the environment of the remaining  $\text{Fe}^{3+}$  ions

is not changed appreciably. For  $\text{Fe}^{3+}$ , plots of Q.S. against  $b^{-3}$  (Figures 3 and 4) are approximately linear. Structural changes involving very large distortions of the octahedra, leading to a change in coordination number, such as are brought about by dithionite reduction of  $\text{Fe}^{3+}$  in nontronites or dehydroxylation of smectites, destroy the linear relationship. The plots can be used to detect such deviations and may thus provide some information about the history of the samples.

Differences between the isomer shifts show that  $\text{Fe}^{3+}$  ions in M(2) sites of montmorillonites and beidellites are more covalently bonded than in M(1). The smaller the difference in covalency between  $\text{Fe}^{3+}$  in the two sites, the more  $\text{Fe}^{3+}$  ions occupy M(1) sites. It appears that the tendency to form covalent bonds is one of the factors governing the distribution of  $\text{Fe}^{3+}$  in the octahedral sheets of these minerals. The relative importance of other factors, e.g. entropy or structural inheritance, is not known at present. In nontronites, for which all the isomer shifts are similar, both M(1) and M(2) sites are populated, but the distribution of  $\text{Fe}^{3+}$  is determined by factors other than the tendency to form covalent bonds.

*Acknowledgements*—We are greatly indebted to Prof. R. Bauminger of the Dept. of Physics, Hebrew University, for her assistance with the Mössbauer spectra and their interpretation. We also wish to thank Dr. A. Bystrom-Brusewitz of the Geological Survey of Sweden and Dr. Sieffermann of O.R.S.T.O.M., France, for donation of the beidellites and volkonskoite respectively. Our thanks are also due to the anonymous reviewer for his constructive criticism.

#### REFERENCES

- Bailey, S. W. (1975) Cation ordering and pseudosymmetry in layer silicates: *Am. Miner.* **60**, 175–187.
- Bancroft, G. M. (1974) *Mössbauer Spectroscopy—An Introduction for Inorganic Chemists and Geochemists*: McGraw-Hill, New York.
- Besnus, Y., Fusil, G., Janet, C., Pinta, M. and Sieffermann, G. (1975) Characteristics of some ultrabasic rocks in Bahia State, Brazil: nontronites, chlorites and chromiferous talc: *Proc. Int. Clay Conf. Mexico City, Mexico*, 27–34.
- Brunot, B. (1973) Application of the Mössbauer effect to the study of clay minerals. Hydrothermal nontronite and nontronite from Lake Malawi: *Neues Jahrb. Mineral. Monatsh.* 452–461.
- Bystrom-Brusewitz, A. M. (1975) Studies of the Li test to distinguish between beidellite and montmorillonite: *Proc. Int. Clay Conf. Mexico City, Mexico*, 419–428.
- Coey, J. M. D. (1975) Iron in a post-glacial lake sediment core: a Mössbauer effect study: *Geochim. Cosmochim. Acta* **39**, 401–415.
- Cousins, D. R. and Dharmawardena, K. G. (1969) Use of Mössbauer spectroscopy in the study of ancient pottery: *Nature* **223**, 732–733.
- Ernst, W. G. and Wai, C. M. (1970) Mössbauer, infrared, X-ray and optical study of cation ordering and dehydrogenation in natural and heat-treated sodic amphiboles: *Am. Miner.* **55**, 1226–1258.
- Frenkel, M. (1975) The mineralogical and chemical properties of the bentonite from Makhtesh Ramon: Ph.D. thesis, The Hebrew University, Jerusalem.
- Goodman, B. A., Russell, J. D., Fraser, A. R. and Woodhams, F. W. D. (1976) A Mössbauer and i.r. spectroscopic study of the structure of nontronite: *Clays & Clay Minerals* **24**, 53–59.
- Güven, N. and Burnham, C. W. (1967) The crystal structure of 3T muscovite: *Z. Kristallogr.* **18**, 502–510.
- Güven, N. and Pease, R. V. (1975) Selected area electron diffraction studies on beidellite: *Clay Minerals* **10**, 427–435.
- Hogg, C. S. and Meads, R. E. (1970) The Mössbauer spectra of several micas and related minerals: *Miner. Mag.* **37**, 606–614.
- Kohyama, N. and Hayashi, H. (1972) Oxygen consumption of clay minerals in the Quarry at Oya, Utsunomiya City, Tochigi Prefecture, Japan: *Ind. Health* **10**, 24–51.
- Malathi, M. and Puri, S. P. (1969) Mössbauer studies of iron in illite and montmorillonite: *J. Phys. Soc. Japan* **26**, 680–683.
- Mering, J. and Oberlin, A. (1971) *The Electron Optical Investigation of Clays* (Edited by J. A. Gard), pp. 193–230: Mineralogical Society, London.
- Mitchell, B. D. and Mackenzie, R. C. (1954) Removal of free iron oxide from clays: *Soil Sci.* **77**, 173–183.
- O'Nions, R. K. and Smith, D. G. W. (1973) Bonding in silicates: an assessment of bonding in orthopyroxene: *Geochim. Cosmochim. Acta* **37**, 249–257.
- Radoslovich, E. W. and Norrish, K. (1962) The cell dimensions and symmetry of layer lattice silicates. Some structural considerations: *Am. Miner.* **47**, 599–616.
- Rozenson, I. and Heller-Kallai, L. (1976) Reduction and oxidation of  $\text{Fe}^{3+}$  in dioctahedral smectites. Part I: reduction with hydrazine and dithionite: *Clays & Clay Minerals* **24**, 271–282.
- Taylor, G. L., Ruotsala, A. P. and Keeling, R. O., Jr. (1968) Analysis of iron in layer silicates by Mössbauer spectroscopy: *Clays & Clay Minerals* **16**, 381–391.
- Tennakoon, D. T. B., Thomas, J. M. and Tricker, M. J. (1974) The surface and intercalate chemistry of layered silicates—II: A  $^{57}\text{Fe}$  Mössbauer study of the role of lattice-substituted iron in benzidine-blue reaction of montmorillonite: *J. Chem. Soc. Dalton*, 2211–2215.
- Wardle, R. and Brindley, G. W. (1972) The crystal structure of pyrophyllite, 1Tc, and of its dehydroxylate: *Am. Miner.* **57**, 732–750.
- Weaver, C. E., Wampler, J. M. and Pecuil, T. E. (1967) Mössbauer analysis of iron in clay minerals: *Science* **156**, 504–508.